

This is the author's final, peer-reviewed manuscript as accepted for publication (AAM). The version presented here may differ from the published version, or version of record, available through the publisher's website. This version does not track changes, errata, or withdrawals on the publisher's site.

Methyl tunnelling of adsorbed methoxy on alumina catalysts

Stewart F Parker, Victoria Garcia Sakai, David Lennon,
Alice Jackson, Mark R Johnson and
Upali A Jayasooriya

Published version information

Citation: Parker, SF et al. "Methyl tunnelling of adsorbed methoxy on alumina Catalysts." Chemical Communications, vol. 52, no. 2 (2016): 366-369.

doi: [10.1039/C5CC08223D](https://doi.org/10.1039/C5CC08223D)

This version is made available in accordance with publisher policies. Please cite only the published version using the reference above.


This item was retrieved from **ePubs**, the Open Access archive of the Science and Technology Facilities Council, UK. Please contact epubs@stfc.ac.uk or go to <http://epubs.stfc.ac.uk/> for further information and policies.

ChemComm

Accepted Manuscript



This article can be cited before page numbers have been issued, to do this please use: S. Parker, V. Garcia Sakai, D. Lennon, A. Jackson, M. Johnson and U. A. Jayasooriya, *Chem. Commun.*, 2015, DOI: 10.1039/C5CC08223D.



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

COMMUNICATION

Methyl tunnelling of adsorbed methoxy on alumina catalysts†

Cite this: DOI: 10.1039/x0xx00000x

Stewart F. Parker,^{*,a,b} Victoria García Sakai,^a David Lennon,^{b,c} Alice Jackson,^d Mark R. Johnson^d and Upali A. Jayasooriya^e

Received 00th January 2012,

Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

The aim of this paper is to investigate whether the methyl group of the adsorbed methoxy intermediate on industrial grade alumina catalysts undergoes rotational tunnelling on the wavenumber energy scale. The data show that this is clearly the case for a fraction of the methyl groups and potentially allows the subtle intermolecular interactions between adsorbed species and catalyst to be probed through the exponential dependence of the tunnel frequency on the rotational potential.

Heterogeneous catalysis is a key economic driver in advanced nations.¹ It is integral to processes that range from crude oil refining to fine chemical and pharmaceutical production.² Hence there is enormous interest and effort in optimising catalyst performance.

Alumina is ubiquitous in heterogeneous catalysis, where it is used as an actual catalytic material or as a catalyst support material.³ In fact, due to its general availability, structural stability and ability to be prepared in a variety of pore size distributions, alumina is the most widely used catalyst support material.

The interaction of methanol with alumina is important in the industrial manufacture of methyl chloride, where methanol and hydrogen chloride are combined over high surface area alumina catalysts:



We have previously investigated this reaction with infrared and inelastic neutron scattering (INS) spectroscopies.⁴⁻⁶ The key intermediate is adsorbed methoxy, $\text{CH}_3\text{O}\equiv$.

“Rotational tunnelling describes the phenomenon of the librational states of a molecule whose rotating atoms are indistinguishable, *e.g.*, all protons, being multiplets. The splitting between the substates is called tunnel splitting”.⁷ Thus for a methyl group, the protons essentially ‘circulate’ between the equivalent positions. If the protons are labelled 1,2,3 then the methyl group

rotation $123 \rightarrow 231 \rightarrow 312 \rightarrow \text{etc.}$ between the equivalent orientations has a tunnel frequency, ω_t , which is largely determined⁷ by the amplitude of the rotational potential, V :

$$\hbar\omega_t = \beta \exp\left(-\alpha\sqrt{\frac{|V|}{B}}\right) \quad (2)$$

where B is the rotational constant, $\beta \approx 2B$, $\alpha \approx 1$. The exponential dependence of the tunnel frequency on the rotational potential is illustrated in Figure 1, which shows the tunnelling and libration frequencies obtained by solving Schrödinger’s equation for rotational motion in a 3-fold potential, of form $\cos(3\phi)$, where ϕ is the methyl group rotation angle and $B = 5.25 \text{ cm}^{-1}$: this makes tunnelling spectroscopy uniquely sensitive to the weak interactions governing rotation.

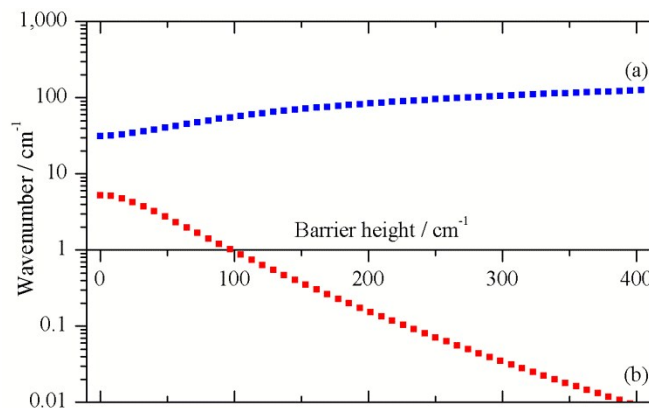


Fig. 1 The librational (a) and tunnelling (b) energies calculated as a function of the barrier height, V , for a 3-fold rotational potential.

To our knowledge, this is the first time tunnelling has been looked for on a real catalyst, although Larese *et al* have extensively studied physisorbed methane on (essentially) single crystal MgO.⁸

Fig. 2 shows the INS spectrum of η -alumina after reaction with methanol at 373 K. The peaks at 2990, 1456 and 1164 cm^{-1} are assigned as the C–H stretch, bend and rock of the methyl group and confirms the presence of chemisorbed methoxy.⁵ The peaks at 3600 and 872 cm^{-1} are assigned as the O–H stretch and bend of residual hydroxyls on the alumina.⁴

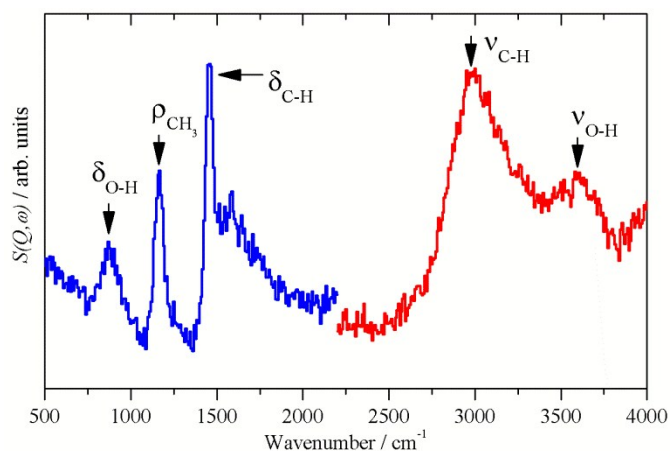


Fig. 2 INS spectrum of methoxy chemisorbed on η -alumina.

Fig. 3 shows the quasielastic neutron scattering (QENS) spectra at 2 K of clean γ -alumina and after reaction with methanol at 373 K to generate methoxy. It is apparent that there is a marked broadening of the central peak showing that there is additional motion in the system. Comparison of methoxy on η - and γ -alumina, Fig. 4, shows both materials behave similarly, the greater intensity of the η - Al_2O_3 spectrum arising partly because it has a larger surface area and a greater density of active sites for strong chemisorption, hence the quantity of adsorbed methoxy is greater for η - Al_2O_3 than for γ - Al_2O_3 . As discussed below, the fraction of sites with low enough rotational barriers to give a tunnelling signal in this energy range must also be taken into consideration.

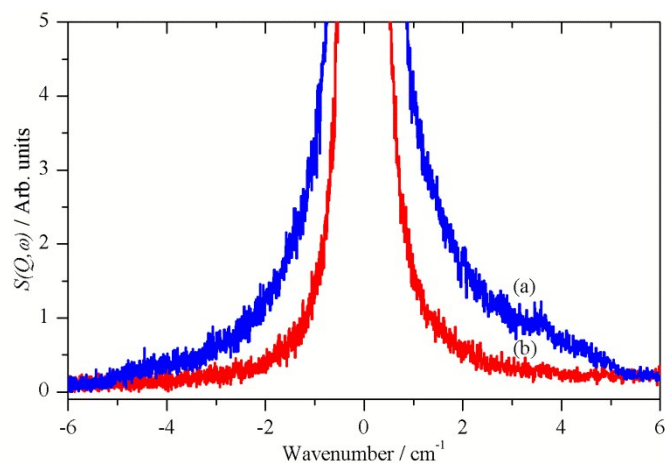


Fig. 3 QENS spectra at 2 K of γ -alumina (a) after reaction with methanol to generate methoxy (blue) and (b) clean (red)

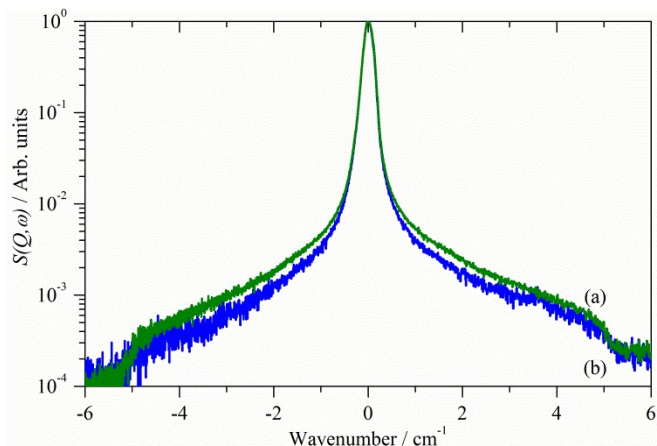


Fig. 4 Comparison of the QENS spectra at 2 K of η -alumina (olive) and (b) γ -alumina (blue) after reaction with methanol to generate methoxy.

As shown in Fig. 5a, in addition to the apparent quasielastic broadening, there is an additional feature at $\sim 24 \text{ cm}^{-1}$. A feature at 45 cm^{-1} , is also present in the clean γ -alumina, Fig. 5b, the same features are seen for η - Al_2O_3 .

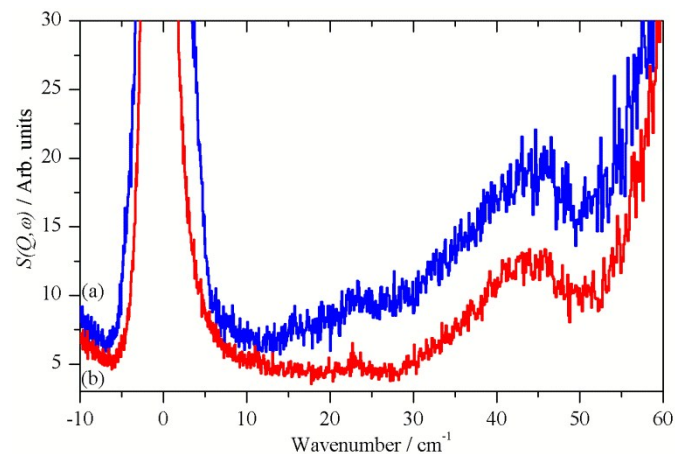


Fig. 5 QENS spectra at 2 K in an extended spectral range of γ -alumina (a) after reaction with methanol to generate methoxy (blue) and (b) clean (red).

The intensity of neutron scattering spectra is strongly dependent on the incoherent cross section, σ , of the scattering atoms. This property is both element and isotope dependent and in particular $\sigma(^1\text{H}) = 80.26 \text{ barn}$ ($1 \text{ barn} = 1 \times 10^{-28} \text{ m}^2$) while $\sigma(^2\text{H}) = 2.05 \text{ barn}$. Thus, by using selectively deuterated methanol, it is possible to determine the origin of the scattering. Fig. 6a shows the results for the reaction of CH_3OD and 6b for CD_3OH with η -alumina. While the profile from reaction with CH_3OD (trace (a)) is very similar to those obtained with CH_3OH , Figs. 3 and 5, reaction with CD_3OH (trace (b)) results in almost no additional scattering, which demonstrates that all the features are due to methoxy, OH produced by the reaction has no effect in this energy region. (Chemisorption of methoxy and methoxy- D_3 was confirmed by INS spectroscopy, see Figs. S1 and S2 of the ESI).

The data clearly show that chemisorption of methoxy on either alumina results in significant changes in the very low energy region. The peak at $\sim 24 \text{ cm}^{-1}$ is assigned to surface modes of the alumina that acquire intensity because they result

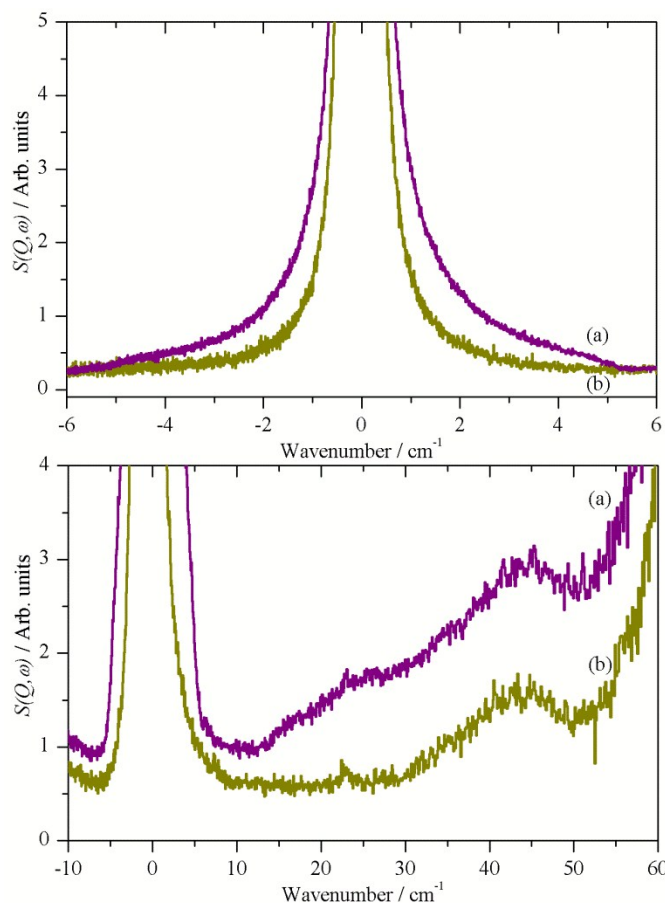


Fig. 6 QENS spectra at 2 K in a narrow (upper) and a wide (lower) energy range of the reaction products of selectively deuterated methanol with η - Al_2O_3 : (a) CH_3OD (purple) and (b) CD_3OH (khaki).

in motion of the methoxy – ‘riding modes’. A calculation⁵ at the Γ -point of methoxy on η -alumina predicts such modes around 16 cm^{-1} , non-zone centre modes (which are observable by INS spectroscopy) are also a possible assignment. The feature at 45 cm^{-1} , which is present in all the spectra before and after reaction with methanol must be assigned to a bulk alumina phonon.

The broadening present in Figs. 3 - 5a would usually be described as quasielastic scattering due to diffusional processes, however, this possibility can be discarded because it is still present at 2 K, see Fig. 3. Rather, we assign it as the signature of methyl tunnelling of the adsorbed methoxy species. The Lorentzian broadening is indicative of a distribution of adsorption sites giving rise to a continuous range of rotational potentials. From the data shown in Figure 1, tunnelling resolved in the energy range from 0.5 to 6 cm^{-1} corresponds to rotational barriers, $V < 120\text{ cm}^{-1}$. The fraction of sites with such low barriers can be estimated from the librational spectrum of the methyl groups shown in Fig. 7. Assuming, to a first approximation, that libration frequency varies linearly with V and that the inelastic structure factor for librations is independent of their frequency, the spectrum, up to $\sim 200\text{ cm}^{-1}$, reflects directly the distribution of rotational potentials. The tunnelling data corresponds to libration frequencies below 60 cm^{-1} , which represents $\sim 15\%$ of the spectral weight, and therefore adsorbed species, up to 200 cm^{-1} . This result is supported by the relative areas of the quasielastic contribution

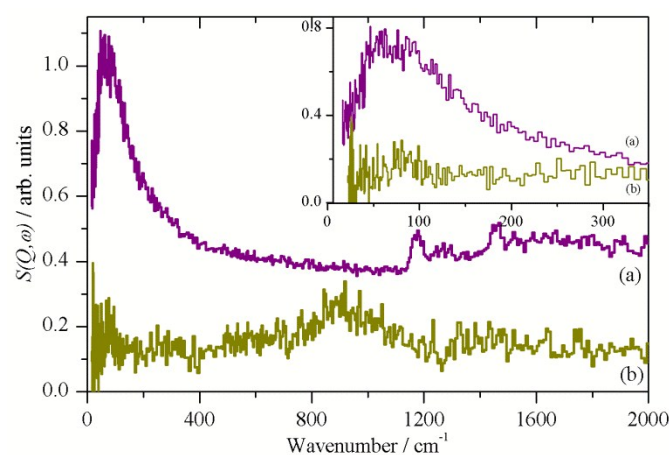


Fig. 7 INS spectra at 20 K the product of the reaction of selectively deuterated methanol with η - Al_2O_3 : (a) CH_3OD (purple) and (b) CD_3OH (khaki). The inset shows the librational region on an expanded scale.

and the total scattering. For both CH_3OH and CH_3OD reacted with η - Al_2O_3 , we find $\sim 15\%$ undergoes rotational tunnelling.

It has been proposed that there are four types of Lewis acid sites on alumina.⁶ Local structure variation around each of these sites would give rise to a distribution of rotational barriers and therefore libration and tunnelling frequencies. According to the assumptions proposed above, the distribution of libration frequencies in Fig. 7 could therefore be fitted with, for example, four independent Gaussian distributions. Clearly the data does not allow this to be done in an unambiguous way, without additional information. Based on a model system of methoxy on η - Al_2O_3 , see Fig. 8, which was used previously to analyse INS spectra in a broad frequency range, we have calculated the potential barrier (V in Eqn. 2) as a function of the rotation of the methyl group. If the methyl group is kept rigid the barrier is $484 - 565\text{ cm}^{-1}$ ($60 - 70\text{ meV}$) (dark blue curve (a) in Fig. 8 lower panel), if the methyl group is allowed to relax the barrier is reduced to $\sim 320\text{ cm}^{-1}$ ($\sim 40\text{ meV}$) (purple curve (b) in Fig. 8 lower panel). Using the relaxed potential, the librational and tunnelling energies are calculated as a function of the barrier height, as shown in Fig. 1. The tunnel splitting is 0.025 cm^{-1} , that is inside the elastic line and therefore not resolved in the quasielastic data, and the librational frequency is 110 cm^{-1} , just beyond the maximum $\sim 75\text{ cm}^{-1}$ of the broad distribution of libration frequencies shown in Fig. 7.

In conclusion, we have shown unequivocally that the methyl group of the adsorbed methoxy intermediate on industrial grade alumina catalysts undergoes rotational tunnelling in the wavenumber energy range. The observed signal corresponds to about 15% of the total amount of methoxy being adsorbed on sites with low barriers for the methyl group rotation. 85% of adsorbed methoxy is on sites with higher rotational potentials for the methyl group, giving rise to the elastic signal in the tunnelling spectra and the distribution of libration frequencies up to $\sim 200\text{ cm}^{-1}$. Calculation of the rotational potential for an established model of an adsorption site of methoxy on alumina confirms the existence of sites with high rotational potentials. A comprehensive computational study is now required to identify and characterise energetically the full set of adsorption sites on alumina. Calculations establish the link between structure and excitations and demonstrate how the tunnelling data presented here can be used to probe the subtle intermolecular interactions between adsorbed species and catalyst. Using other backscattering

COMMUNICATION

spectrometers, with energy resolution of the order of 0.01 cm^{-1} , the observable tunnelling spectrum could be sampled to lower energies.

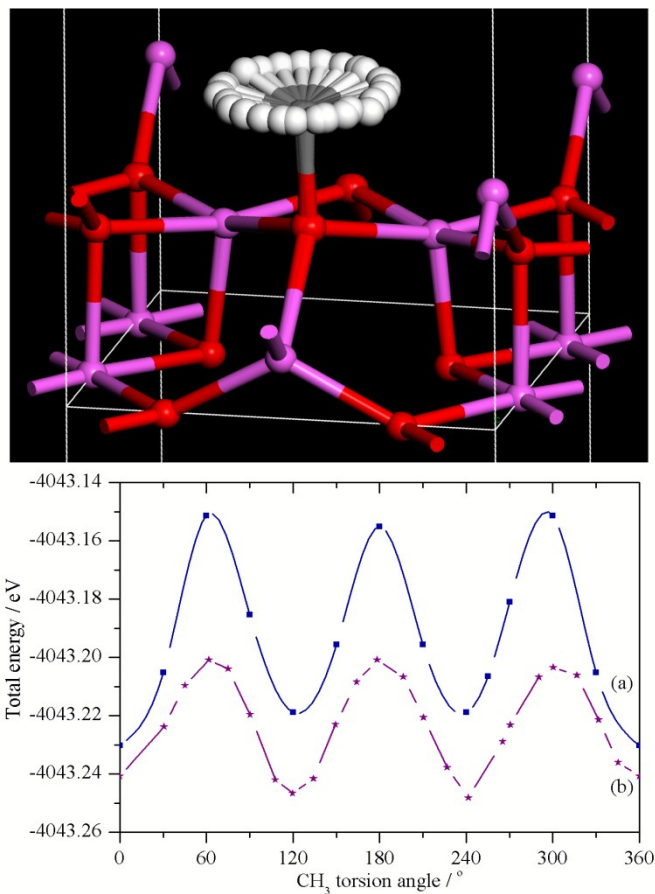


Fig. 8 Upper: model of methoxy on $\eta\text{-Al}_2\text{O}_3$ used to generate the rotational potential. (Magenta = Al, red = O, grey = C, white = H). Lower: rotational potential when: (a) the methyl group is held rigid and (b) when it is allowed to relax. Computational details are given in the ESI.

This work was supported by the UK Catalysis Hub (EPSRC grant no. EP/K014714/1). We thank the STFC Rutherford Appleton Laboratory for access to neutron beam facilities. Experimental assistance and helpful discussions with Dr Franz Demmel and Dr Eugene A. Goremychkin (ISIS Facility) are gratefully acknowledged.

Notes and references

† Dedicated to the memory of Professor Norman Sheppard FRS 1922 – 2015.

^a ISIS Facility, STFC Rutherford Appleton Laboratory, Chilton, Didcot, Oxfordshire OX11 0QX, UK. E-mail: stewart.parker@stfc.ac.uk.

^b UK Catalysis Hub, Research Complex at Harwell, STFC Rutherford Appleton Laboratory, Chilton, Didcot, Oxfordshire OX11 0QX, UK.

^c School of Chemistry, Joseph Black Building, University of Glasgow, Glasgow G12 8QQ, UK

^d Institut Laue-Langevin, 71 Avenue des Martyrs, CS 20156, F - 38042 Grenoble Cedex 9, France.

^e School of Chemistry, Faculty of Science, University of East Anglia, Norwich Research Park, Norwich, Norfolk, NR4 7TJ, UK.

‡ Electronic Supplementary Information (ESI) available: Experimental details (sample preparation and instrumentation), computational methods and assignment of the spectrum of adsorbed methoxy. See DOI: 10.1039/c000000x/

- 1 M. Morbidelli, A. Gavriilidis and A. Varma, *Catalyst Design*, Cambridge University Press, Cambridge, 2001, p 1.
- 2 H.J. Arpe, *Industrial Organic Chemistry*, 3rd ed., Wiley-VCH, Weinheim, 2010.
- 3 R. J. Farrauto and C. H. Bartholomew, *Fundamentals of Industrial Catalytic Processes*, Blackie, London, 1997, p. 60.
- 4 A.R. McNroy, D.T. Lundie, J.M. Winfield, C.C. Dudman, P. Jones, S.F. Parker and D. Lennon, *Catalysis Today*, 2006, **114**, 403.
- 5 A.R. McNroy, D.T. Lundie, J.M. Winfield, C. Dudman, P. Jones, S.F. Parker, J.W. Taylor and D. Lennon, *Phys. Chem. Chem. Phys.*, 2005, **7**, 3093.
- 6 D. Lennon and S.F. Parker, *Acc. Chem. Res.*, 2014, [doi: 10.1021/ar400271c].
- 7 M. Prager and A. Heidemann, *Chemical Reviews*, 1997, **97**, 2934.
- 8 J.Z. Larese, T. Arnold, A. Barbour, L.R. Frazier, *Langmuir*, 2009, **25**, 4078-4083.